arXiv:cond-mat/0212137v1 [cond-mat.supr-con] 6 Dec 2002

Reinterpretation of the equilibrium magnetization of a $Tl_2Ba_2CaCu_2O_{8+x}$ single crystal. Another phase transition in the mixed state of high-T_c superconductors?

I. L. Landau[1,2] H. R. Ott[1]
[1]*Laboratorium für Festkörperphysik, ETH Hönggerberg, CH-8093 Zürich, Switzerland and*
[2]*Kapitza Institute for Physical Problems, 117334 Moscow, Russia*

(Dated: February 1, 2008)

We apply a recently developed scaling procedure for the analysis of the equilibrium magnetization M that was measured on a $Tl_2Ba_2CaCu_2O_{8+x}$ single crystal and was recently reported in the literature. The results of our analysis are distinctly different from those obtained in the original publication where the Hao-Clem model served to analyze the magnetization data. We argue that the Hao-Clem model is not adequate for a quantitative description of the mixed state in high-T_c superconductors especially in high magnetic fields. The scaled equilibrium magnetization data reveal a pronounced kink in the $M(H)$ dependence that might be indicative of a phase transition in the mixed state.

PACS numbers: 74.25.Op, 74.25.Qt, 74.72.-h

First, we briefly review the current situation in the interpretation of magnetization measurements in the mixed state of high-T_c (HTSC) superconductors. The most widely used approach for evaluating the thermodynamic critical field H_c and the Ginzburg-Landau (GL) parameter κ of HTSC's from magnetization data is the Hao-Clem model.[1,2] Using the values of H_c and κ that result from the field dependence of the magnetization measured at different temperatures, the temperature dependence of the upper critical field $H_{c2}(T)$, as well as the magnetic field penetration depth $\lambda(T)$, and the superconducting coherence length $\xi(T)$ may be calculated. However a recent theoretical analysis of the Hao-Clem approach demonstrated that the calculation of the local magnetic induction by a linear superposition of contributions of individual vortices, as it was done in Ref. 2, is quantitatively acceptable only for low magnetic fields.[3,4] A rather direct confirmation of the inadequecy of the Hao-Clem model for the quantitative analysis of experimental results is provided by Figs. 3(a) and 3(b) in Ref. 5 where data on the equilibrium magnetization of Tl-based single crystals were presented and analyzed. The quoted Fig. 3(a) reveals a rather strong increase of κ with increasing temperature, resulting in a very unusual temperature dependence of the upper critical field with H_{c2} being practically temperature independent at low temperatures and almost diverging at temperatures above 85-90 K (Fig. 3(b)). Because this anomalous increase of H_{c2} starts well below the superconducting critical temperature T_c of the investigated sample, it can hardly be ascribed to fluctuation effects. This very strong increase of κ upon approaching the critical temperature is not a feature that was observed in one particular study. It turns out to be a rather universal result if the Hao-Clem model is employed for the analysis of magnetization data.[6,7,8,9,10,11,12,13,14,15,16,17] We argue that the magnetic field dependence of the magnetization at constant temperature provided by the Hao-Clem model is not sufficiently accurate and therefore, a fitting of the relevant theoretical formula to experimental data results in an unphysical temperature dependence of the GL parameter κ, one of the key parameters in the Hao-Clem model. In the GL theory κ is temperature independent and it only slowly decreases with increasing temperature in the framework of microscopic theories.[18,19] Below we show that the quoted experimental data may very well be interpreted by assuming that κ is temperature independent. The temperature dependence of H_{c2} which results from our analysis, is in good agreement with expectations of the GL theory.

Our analysis of the original data which were presented in Ref. 5 is based on a scaling procedure developed in Ref. 20. It was shown that if the GL parameter κ is temperature independent, the equilibrium magnetizations in the mixed state of type-II superconductors at two different temperatures T_0 and T are related by

$$M(H/h_{c2},T_0) = M(H,T)/h_{c2} + c_0(T)H, \qquad (1)$$

with $h_{c2}(T) = H_{c2}(T)/H_{c2}(T_0)$ representing a normalized upper critical field.[20] The first term on the right-hand side of Eq. (1) is universal for any type-II superconductor, while the second one is introduced to account for the temperature dependent paramagnetism of HTSCs in the normal state.[21] In the following we use M_{eff} to denote the magnetization calculated using Eq. (1) in order to distinguish it from direct experimentally measured values of M. The quantities $h_{c2}(T)$ and $c_0(T)$ are the adjustable parameters of the scaling procedure and they are established from the condition that the M_{eff} curves, calculated from the $M(H)$ measurements in the reversible regime at different temperatures, collapse onto a single curve, representing the equilibrium magnetization at $T = T_0$ (see Ref. 20 for details).

It has been shown that the scaling procedure described by Eq. (1) works rather well for different HTSC materials including single crystals and grain-aligned samples,[20] as well as polycrystals and ceramics.[23] An important advantage of this approach is that no particular formula for $M(H)$ has to be assumed *a priori* and therefore, this scaling procedure may be used for any type-II superconduc-

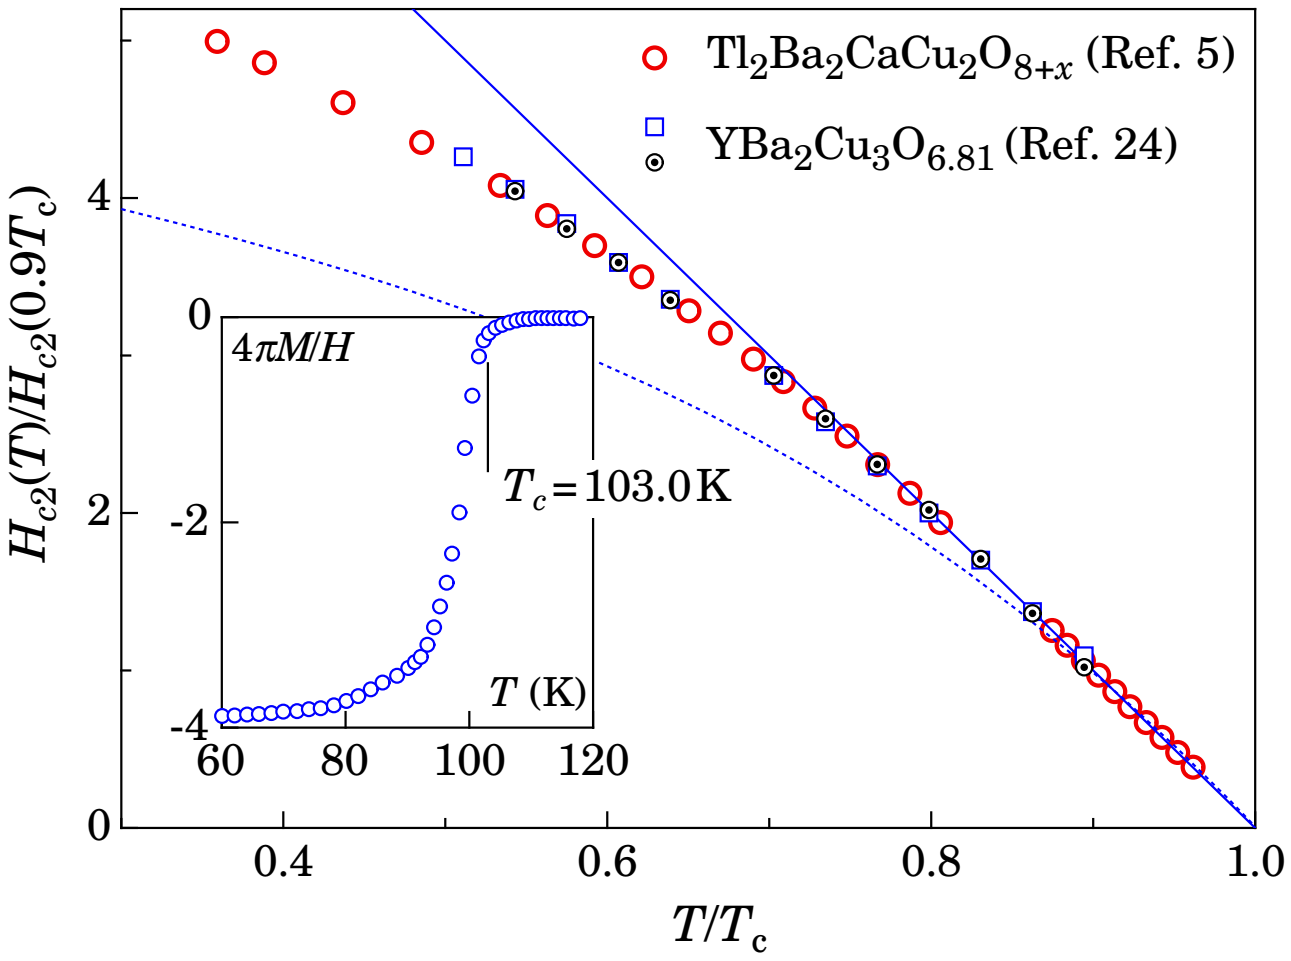

FIG. 1: The dependence of the normalized upper critical field on T/T_c. The solid line is the best linear fit to the data points for $T \geq 90$ K. The dotted line represents the "universal" $h_{c2}(T/T_c)$ curve reported in Ref. 20 for most of the HTSC compounds. The data points for two underdoped YBCO samples with the same oxygen content, investigated in Ref. 24, were taken from Ref. 23. The inset shows the $M(T)$ curve measured at $H = 10$ Oe. The short vertical line indicates the position of T_c as evaluated by the linear extrapolation of $h_{c2}(T)$ to $h_{c2} = 0$.

tor, independent of the pairing type, the absolute value of κ, the anisotropy of superconducting parameters, or the demagnetization factor of the sample.

As has briefly been outlined above (see Ref. 20 for details), Eq. (1) serves to evaluate the temperature variation of the normalized upper critical field $h_{c2}(T)$. It turns out that $h_{c2}(T)$ for this Tl2212 sample varies perfectly linearly with T above 90 K. This linearity allows for a quite accurate evaluation of the critical temperature T_c by extrapolating the $h_{c2}(T)$ curve to $h_{c2} = 0$. The inset of Fig. 1 demonstrates that the value of T_c resulting from this procedure is consistent with the temperature dependence of the low-field magnetization of this sample. The normalized upper critical field h_{c2} versus T/T_c is shown in the mainframe of Fig. 1.

As has been shown in our previous studies,[20,23] all investigated HTSC's may so far be divided into two groups. For each group, the $h_{c2}(T/T_c)$ curves for the individual HTSC compounds turn out to be identical but the as yet identified two universal curves are distinctly different. The major group includes practically all different families of HTSCs, except $Y_2Ba_4Cu_7O_{15}$ and underdoped $YBa_2Cu_3O_{7-x}$ (YBCO) compounds which belong to the other group. As may be seen in Fig. 1, $h_{c2}(T)$ of this particular Tl2212 sample is practically identical with the $h_{c2}(T)$ curves of two underdoped YBCO samples investigated in Ref. 24. This implies that the smaller group is not limited to underdoped Y-based cuprates. It was shown in Ref. 23 that a ceramic Tl2212 sample with $T_c = 107$ K, which was investigated in Ref. 25, belongs to the other group represented by the dotted line in Fig. 1. A possible explanation for this difference between these two Tl-based samples may be sought in the difference of the oxygen content.

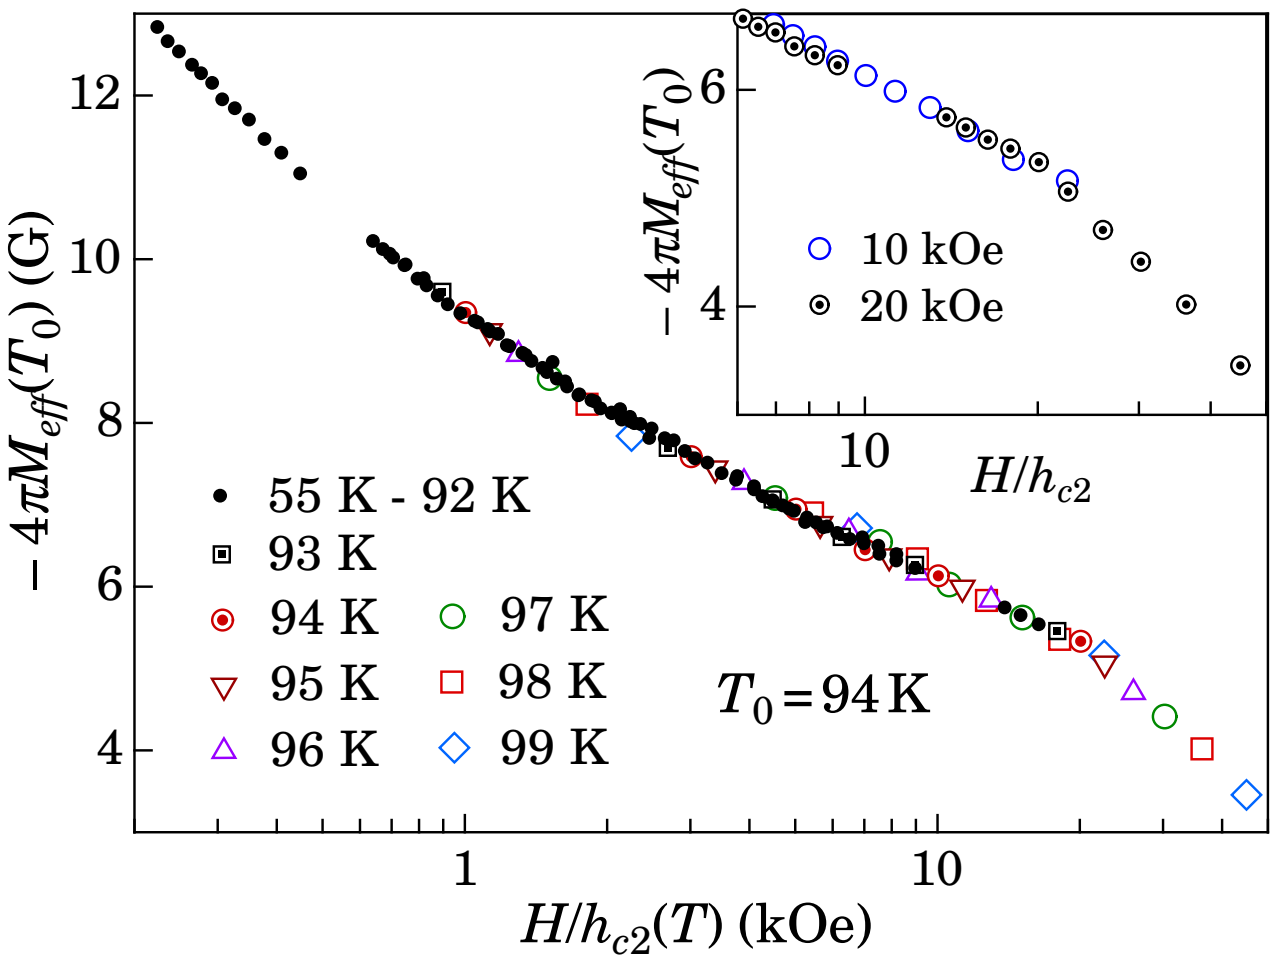

FIG. 2: The scaled magnetization M_{eff} calculated for $T_0 = 94$ K. The inset emphasizes the high field part of M_{eff}.

The dependence of $M_{eff}(T_0)$ on $H/h_{c2}(T)$ that results from our scaling procedure is shown in Fig. 2. Because of the high quality of the experimental data presented in Ref. 5 and the extended covered range of magnetic fields, the scaling is nearly perfect. The $M_{eff}(H)$ data points, calculated from the measurements at different temperatures, combine to a single curve with virtually no deviations. The remarkable feature of this curve is a pronounced kink at $H/h_{c2} \approx 20$ kOe. This kink clearly indicates a significant change in the properties of the mixed state. Unfortunately, the measurements in Ref. 5 are limited to magnetic fields $H \leq 20$ kOe and, as may be seen in Fig. 2, only a limited number of data points, measured at $T \geq 96$ K and $H = 20$ kOe combine to the $M_{eff}(H)$ curve above the kink. This is why on the basis of the available data, no definite conclusions concerning the implications of this observation can be made and further studies are needed to clarify the situation. If this feature will be confirmed by a more detailed study, the kink would definitely reflect some kind of a phase transition.

We conclude that, contrary to the claims of Ref. 5, the magnetization data perfectly well be explained by assuming a temperature independent Ginzburg-Landau parameter κ and a conventional temperature dependence of the upper critical fieldH_{c2}, as shown in Fig. 1.

---

[1] Z. Hao and J. R. Clem, Phys. Rev. Lett. **67**, 2371(1991).

[2] Z. Hao and J. R. Clem, M. W. McElfresh, L.Civale, A. P. Malozemoff, and F. Holtzberg, Phys. Rev. B **43**, 2844 (1991).

[3] W. V. Pogosov, K. I. Kugel, and A. L. Rakhmanov, Zh. Eksp. Teor. Fiz. **118**, 676 (2000) [JETP **91**, 588 (2000)].

[4] W. V. Pogosov, K. I. Kugel, A. L. Rakhmanov, and E. H. Brandt, Phys. Rev. B **64**, 064517 (2001).

[5] Heon-Jung Kim, P. Chowdhury, In-Sun Jo, and Sung-Ik Lee, Phys. Rev. B **66**, 134508 (2002).

[6] Qiang Li, M. Suenaga, Junho Gohng, D. K. Finnemore, T. Hikata, and K. Sato, Phys. Rev. B **46**, 3195 (1992).

[7] J. H. Cho, Zhidong Hao, and D. C. Johnston, Phys. Rev. B **46**, 8679 (1992).

[8] Qiang Li, M. Suenaga, T. Kimura, and K.Kishio, Phys. Rev. B **47**, 2854 (1993).

[9] Qiang Li, M. Suenaga, T. Kimura, and K.Kishio, Phys. Rev. B **47**, 11384 (1993).

[10] D. N. Zheng, A. M. Campbell, and R. S. Liu, Phys. Rev. B **48**, 6519 (1993).

[11] Qiang Li, K. Shibutani, M. Suenaga, I. Shigaki, and R. Ogawa, Physica B **194-196**, 1501 (1994).

[12] Mung-Seog Kim, Sung-Ik Lee, Seong-Cho Yu, and Nam H. Hur, Phys. Rev. B **53**, 9460 (1996).

[13] J. R. Thompson, J. G. Ossandon, D. K. Christen, M. Paranthaman, E. D. Specht, and Y. C. Kim, Phys. Rev. B **54**, 7505 (1996).

[14] Yi Zhuo, Jae-Hyuk Choi, Mung-Seog Kim, Wan-Seon Kim, Z. S. Lim, Sung-Ik Lee, and Sergey Lee, Phys. Rev. B **55**, 12719 (1997).

[15] Mung-Seog Kim, Sung-Ik Lee, Seong-Cho Yu, I. Kuzemskaya, E. S. Itskevich, and K. A. Lokshin, Phys. Rev. B **57**, 6121 (1996).

[16] M. Y. Cheon, G. C. Kim, B. J. Kim, and Y. C. Kim, Physica C **302**, 215 (1998).

[17] Yi Zhuo, Su-Mi Oh, Jae-Hyuk Choi, Mun-Seog Kim, Sung-Ik Lee, N. P. Kiryakov, M. S. Kuznetsov, and Sergey Lee, Phys. Rev. B **60**, 13094 (1999).

[18] L. P. Gor'kov, Zh. Eksp. Teor. Fiz. **37**, 833 (1959) [Soviet Phys.-JETP **10**, 593 (1960)].

[19] E. Helfand and N. R. Werthamer, Phys Rev. **147**, 288 (1966).

[20] I. L. Landau and H. R. Ott, Phys. Rev. B **66**, 144506 (2002).

[21] As is discussed in more detail in Ref. 20, if the measurements are made at temperatures close to the superconducting critical temperature, the term $c_0(T)H$ may also account for the contribution to the sample magnetization arising from fluctuation effects. However, because this contribution is not really linear in H, it can only approximately be accounted for. At low temperatures and magnetic fields well below H_{c2} the flactuation induced contribution to the sample magnetization is negligible.

[22] I. L. Landau and H. R. Ott, to be published in J. Low Temp. Phys. (cond-mat/0207670).

[23] I. L. Landau and H. R. Ott, Physica C in print (cond-mat/0209684).

[24] M. Däumling, Physica C **183**, 293 (1991).

[25] G. Triscone, A. F. Khode, C. Opagiste, J.-Y. Genoud, T. Graf, E. Janod, T. Tdukamoto, M. Couach, A. Junod, and J. Muller, Physica C **224**, 263 (1994).